



# SANDVIK HIGH-N FOR MEDICAL APPLICATIONS

## TUBE AND PIPE, SEAMLESS

### DATASHEET

Sandvik High-N is a molybdenum and nitrogen alloyed austenitic stainless steel, used for orthopedic implants and fracture fixation devices.

The grade is characterized by:

- Proof strength is up to twice that of Sandvik 316LVM in the annealed condition
- Higher corrosion resistance than Sandvik 316LVM
- High microcleanliness
- Very good surface finish
- Good forgeability

#### STANDARDS

- UNS: S31675
- BS: 7252-9

#### Product standard

- ASTM F1586

#### CHEMICAL COMPOSITION (NOMINAL) %

##### Chemical composition (nominal) %

C	Si	Mn	P	S	Cr	Ni	Mo	Cu	N	Nb
≤0.06	≤0.60	4.0	≤0.025	≤0.003	20.5	9.5	2.4	≤0.20	0.4	0.3

#### FORMS OF SUPPLY


##### Tube

- Bright annealed
- Cold finished
- Ground outside surface

##### Tolerances

The tolerances for OD and ID, eccentricity and straightness are determined in accordance with customers' requirements.

Sandvik standard: OD and ID  $\pm 0.04$  mm (0.0016 in.); eccentricity max. 5%

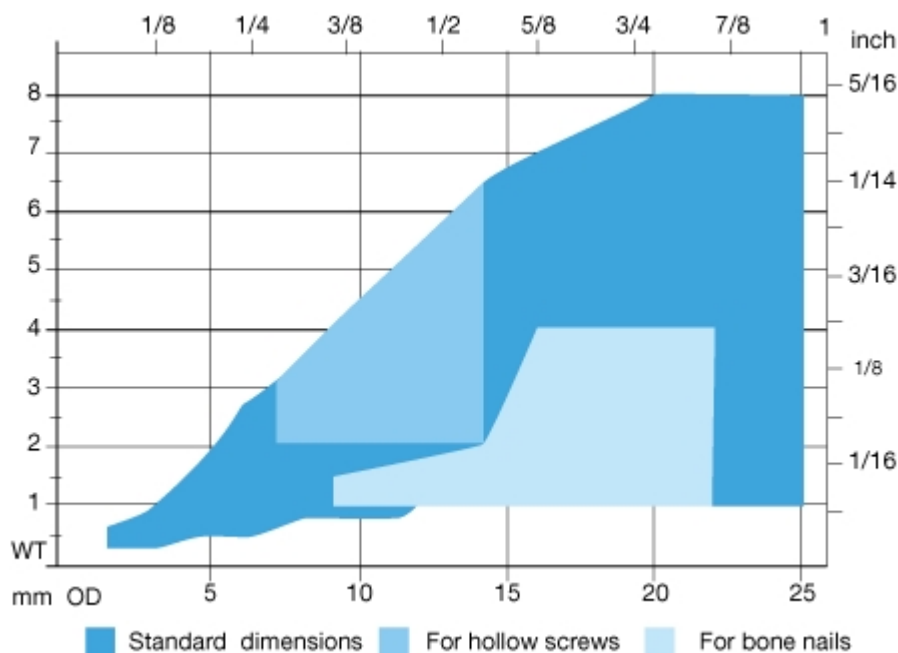

### Other product forms

Sandvik High-N can also be supplied as bar (round and flat) and wire.

### MECHANICAL PROPERTIES

Product	Condition	Tensile strength	Proof strength	Elongation A,		
		R <sub>m</sub>	R <sub>p0,2</sub>	%		
		MPa	ksi	MPa	ksi	
		min	min	min	min	typical
Wire		1500 max	217 max			
Bar	Annealed	740	107	430	62	35
Bar	Medium	1000	145	700	102	20
Bar	Hard	1100	160	1000	145	10
Tube, thick wall	Bright annealed	740	107	430	62	min 35
Tube, thick wall	Cold finished	1200	174	1100	160	min 10

Specific tensile requirements available on request

### PHYSICAL PROPERTIES

Property		
Density ( 20 °C)	8.0 g/cm <sup>3</sup>	0.29 lb/in <sup>3</sup>
Modulus of elasticity, x10 <sup>3</sup> (20°C)	200 MPa	29.0ksi
Specific heat capacity (20°C)	485 J/(kg °C)	0.11Btu/(lb°F)
Thermal conductivity (20°C)	14W /(m°C)	8 Btu/(ft h °F)
Thermal expansion, x10 <sup>-6</sup> (30-100°C)	16.5 per °C	9.5 per °F

### CORROSION RESISTANCE

Sandvik High-N has a very good resistance in physiological environments to:

- General and intergranular corrosion due to high purity and low ferrite content
- Pitting and crevice corrosion due to the high molybdenum content

Sandvik High-N is capable of passing the Money penny Strauss corrosion test in accordance with ISO / ASTM requirements.

### MACHINING

	Hardness	Cutting speed range	Feed range		
		SFM	m/min	IPR	mm/rev
Turning	250-400	885-145	270-45	0.002-0.024	0.05-0.6
Milling	250-400	855-245	260-75	0.002-0.016	0.05-0.4
Drilling	250-400	115-195	35-60	0.002-0.012	0.05-0.3

Disclaimer: Sandvik is not providing any products or services that are intended or may be construed to be recommending or otherwise advising on, in any manner, the design, suitability, appropriateness or effectiveness, from a medical/biological/safety perspective, of any medical material, instrument and/or medical device.